

A Simple Efficient Finite Element for the Sandwich and Laminated Composites Plates Analysis

1st Khmissi BELKAID
*Research Center in Industrial
Technologies CRTI*
P.O.Box 64, Cheraga 16014
Algiers, Algeria
khmissi.belkaid85@gmail.com

2nd 1st Badreddine Boubir
*Research Center in Industrial
Technologies CRTI*
P.O.Box 64, Cheraga 16014
Algiers, Algeria)
boubir11@gmail.com

3rd Gaagaia Djamel Edinne
*Research Center in Industrial
Technologies CRTI*
P.O.Box 64, Cheraga 16014
Algiers, Algeria)
d.gaagaia@crti.dz

4nd Aouaichia Hamza
*Research Center in Industrial
Technologies CRTI*
P.O.Box 64, Cheraga 16014
Algiers, Algeria)
h.aouaichia@crti.dz

5nd Fergani Nadir
*Research Center in Industrial
Technologies CRTI*
P.O.Box 64, Cheraga 16014
Algiers, Algeria)
n.fergani@crti.dz

6nd Boutasseta Nadir
*Research Center in Industrial
Technologies CRTI*
P.O.Box 64, Cheraga 16014
Algiers, Algeria)
n.boutasseta@crti.dz

Abstract— In this work, the theory of Reddy's third order shear deformation Kinematic and from the equivalent approach single layer are used in order to suggest a simple efficient finite element for the analysis of isotropic and composite laminated and sandwich plates. The proposed element is an isoparametric 2D quadrilateral C0 four-node with seven degrees of freedom (7DOF) per node, three translation, two rotations and two higher order rotational degrees. The selective numerical integration technique is presented for the formulation in order to improve the performance of model and to surmount the locking problem in thin plate case. Furthermore, the performance and reliability of the proposed model are investigated by comparing the author's results with those obtained using the three-dimensional elasticity theory, analytical solutions and other advanced finite element models.

Keywords— *Third Order Shear Deformation Theory; Laminated Composite Plates; Finite Element; Bending Behavior;*

I. INTRODUCTION

Nowadays, the multilayer composite materials have found increasingly wide applications essentially in all industrial sectors, such as aerospace, automotive, civil engineering and shipbuilding. This considerable use is probably due to the remarkable benefits of this type of materials namely; an excellent rigidity weight, good corrosion resistance, fatigue resistance and many more advantages particularly since their properties are adjustable for different situations. A review was published by Mouritz et al. [1] for the recent applications of composite structures and their developments on the ships and submarines. On the other hand, the analysis of multilayer composite structures is still questionable and soliciting accurate theories about complicated to describe

their behavior and different mechanical phenomena. For example, modeling thick multilayer structures requires refined theories taking into account good expression of the effect due to the transverse shear deformation through their thicknesses and in particular the interlaminar. Therefore, several theories take into account the transverse shear effect on the analysis of multilayer composite structures that are the extension of the equivalent single layer approach [2]. The classical laminated plate theory (CLPT) [3, 4] is one of the oldest and simplest theories in describing the deformation of the plates. However, it is adequate for the analysis thin structures because of the negligence of the effect due to the transverse shear. While, the simplest theory which takes into account the deformation of transverse shear is the first order shear deformation theory [FSDT] [5, 6]. However, these theories require to correction factors [6-9]. Consequently, theories of higher order shear deformation (HSDT) have been proposed in the literature [10, 11], in accurately assessing the deformation and stress of transverse shear multilayer plates without to need factors correction. Moreover, the theory of Reddy (TSDT) is the higher order theory most frequent for multilayer plates analysis when it is able to assess the stresses and transverse shear deformations with a small number unknown and do not depend on the layer number [12, 13]. However, the third order theory of Reddy [TSDT] encounters a problem when finites elements are applied by requiring the second derivative C_1 [14], it is identical in the finite elements development of thin plate based on the classical theory [15]. Therefore, many of finite element models (2D) based on Reddy's third order theory were proposed in the literature and in various geometries and nodes, and thus different number of degrees of freedom [16] for the analysis the static behavior of laminated

composite plates. A review has published by Zhang and Yang (2009) [16] contains a recent development finite element for the analysis of laminated composite plates.

The objective of this paper is the development a new simple finite element less expensive in terms of accuracy and stability on the basis of Reddy's third order theory (TSDT) by adopting the approach of equivalent single layer, and able to analyze the bending behavior of isotropic and laminated composite plates by ensuring the right compromise between the cost and precision.

II. KINEMATIC

The displacement field according the Reddy's third order shear deformation theory (TSDT) [12] can be expressed as follows:

$$\begin{aligned} u_1 &= u + z\psi_x - \frac{4z^3}{3h}(\psi_x + \frac{\partial w}{\partial x}), \\ u_2 &= v + z\psi_y - \frac{4z^3}{3h}(\psi_y + \frac{\partial w}{\partial y}), \\ u_3 &= w \end{aligned} \quad (1)$$

Where u, v, w are the displacements to the median plane of the plate and ψ_x, ψ_y are rotations about the axes y and x respectively, and h is the thickness of the plate. The deformations associated with displacement field (1), given as follows:

$$\begin{aligned} \varepsilon_{11} &= \frac{\partial u_1}{\partial x} + \frac{1}{2} \left[\left(\frac{\partial u_3}{\partial x} \right)^2 \right] = \varepsilon_1^0 + z(\kappa_1^0 + z^2 \kappa_1^2); \\ \varepsilon_{22} &= \frac{\partial u_2}{\partial y} + \frac{1}{2} \left[\left(\frac{\partial u_3}{\partial y} \right)^2 \right] = \varepsilon_2^0 + z(\kappa_2^0 + z^2 \kappa_2^2); \\ \varepsilon_{23} &= \left(\frac{\partial u_2}{\partial z} + \frac{\partial u_3}{\partial y} + \frac{\partial u_3}{\partial y} \frac{\partial u_3}{\partial z} \right) = \varepsilon_4^0 + z^2 \kappa_4^2; \\ \varepsilon_{13} &= \left(\frac{\partial u_1}{\partial z} + \frac{\partial u_3}{\partial x} + \frac{\partial u_3}{\partial x} \frac{\partial u_3}{\partial z} \right) = \varepsilon_5^0 + z^2 \kappa_5^2; \\ \varepsilon_{12} &= \left(\frac{\partial u_1}{\partial y} + \frac{\partial u_2}{\partial x} + \frac{\partial u_3}{\partial x} \frac{\partial u_3}{\partial y} \right) = \varepsilon_6^0 + z(\kappa_6^0 + z^2 \kappa_6^2); \end{aligned} \quad (2)$$

III. THE CONSTITUTIVE EQUATIONS

The stress-strain relationships laminated to the k -ième layer after the global coordinate x, y, z transformation [17] and according the transformation matrix and the stress-strain relationships, it is given by:

$$\begin{aligned} \begin{Bmatrix} \sigma_{xx} \\ \sigma_{yy} \\ \sigma_{xy} \end{Bmatrix}_k &= \begin{bmatrix} \bar{C}_{11} & \bar{C}_{12} & \bar{C}_{16} \\ \bar{C}_{12} & \bar{C}_{22} & \bar{C}_{26} \\ \bar{C}_{16} & \bar{C}_{26} & \bar{C}_{66} \end{bmatrix} \begin{Bmatrix} \varepsilon_{xx} \\ \varepsilon_{yy} \\ \gamma_{xy} \end{Bmatrix}_k \\ \begin{Bmatrix} \sigma_{yz} \\ \sigma_{xz} \end{Bmatrix}_k &= \begin{bmatrix} \bar{C}_{44} & \bar{C}_{45} \\ \bar{C}_{45} & \bar{C}_{55} \end{bmatrix} \begin{Bmatrix} \gamma_{yz} \\ \gamma_{xz} \end{Bmatrix}_k \end{aligned} \quad (3)$$

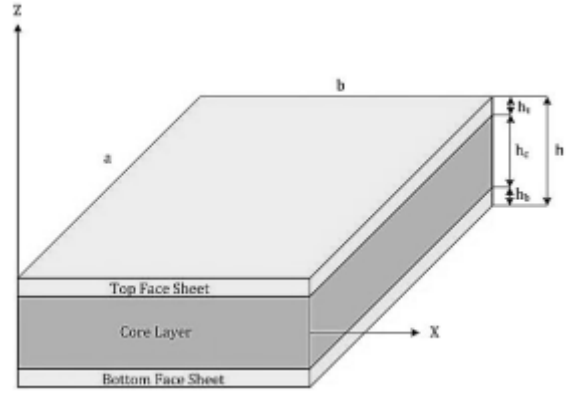


Fig. 1 Geometry and coordinate system of the laminated composite plate

IV. VIRTUAL WORK PRINCIPLE

The static equations of the theory can be derived from the virtual work principle [12] by expressing the strain variation energy as follows:

$$\int_{-h/2A}^{h/2} (\sigma_1 \delta \varepsilon_1 + \sigma_2 \delta \varepsilon_2 + \sigma_6 \delta \varepsilon_6 + \sigma_5 \delta \varepsilon_5 + \sigma_4 \delta \varepsilon_4) dAdz + \int_A q \delta w dA = 0 \quad (4)$$

According to the substitution of equations (2) in the static equation (4) we obtain:

$$\begin{aligned} \int_A [N_1 \frac{\partial \delta u}{\partial x} + M_1 \frac{\partial \delta \psi_x}{\partial x} + P_1 (-\frac{4}{3h^2} (\frac{\partial \delta \psi_x}{\partial x} + \frac{\partial^2 \delta w}{\partial x^2})) + N_2 \frac{\partial \delta v}{\partial y} + M_2 \frac{\partial \delta \psi_y}{\partial y} + \\ P_2 (-\frac{4}{3h^2} (\frac{\partial \delta \psi_y}{\partial y} + \frac{\partial^2 \delta w}{\partial y^2})) + N_6 (\frac{\partial \delta u}{\partial y} + \frac{\partial \delta v}{\partial x}) + M_6 (\frac{\partial \delta \psi_x}{\partial y} + \frac{\partial \delta \psi_y}{\partial x}) + \\ P_6 (-\frac{4}{3h^2} (\frac{\partial \delta \psi_x}{\partial y} + \frac{\partial \delta \psi_y}{\partial x} + 2 \frac{\partial^2 \delta w}{\partial x \partial y})) + Q_2 (\delta \psi_y + \frac{\partial \delta w}{\partial y}) + R_2 (-\frac{4}{h^2} (\delta \psi_y + \frac{\partial \delta w}{\partial y})) \\ + Q_1 (\delta \psi_x + \frac{\partial \delta w}{\partial x}) + R_2 (-\frac{4}{h^2} (\delta \psi_x + \frac{\partial \delta w}{\partial x})) + q \delta w] dA = 0 \end{aligned} \quad (5)$$

Where N_i, M_i, P_i, Q_i, R_i and R_1, R_2 are the resulting forces to define:

$$(N_i, M_i, P_i) = \sum_{k=1}^n \int_{h_{k-1}}^{h_k} \sigma_i(1, z, z^3) dz; \quad (i=1, 2, 6);$$

$$(Q_2, R_2) = \sum_{k=1}^n \int_{h_{k-1}}^{h_k} \sigma_4(1, z^2) dz; \quad (Q_1, R_1) = \sum_{k=1}^n \int_{h_{k-1}}^{h_k} \sigma_5(1, z^2) dz;$$

Therefore, the generalized relations resulting forces can be given as follows [12]:

$$\begin{aligned} \begin{Bmatrix} \{N_i\} \\ \{M_i\} \\ \{P_i\} \end{Bmatrix} &= \begin{bmatrix} [A_{ij}] & [B_{ij}] & [E_{ij}] \\ & [D_{ij}] & [F_{ij}] \\ sym & & [H_{ij}] \end{bmatrix} \begin{Bmatrix} \varepsilon^0 \\ \kappa^0 \\ \kappa^2 \end{Bmatrix} \\ \begin{Bmatrix} \{Q_2\} \\ \{Q_1\} \\ \{R_2\} \\ \{R_1\} \end{Bmatrix} &= \begin{bmatrix} A_{44} & A_{45} & D_{44} & D_{45} \\ & A_{55} & D_{45} & D_{55} \\ & & F_{44} & F_{45} \\ sym & & & F_{55} \end{bmatrix} \begin{Bmatrix} \varepsilon_4^0 \\ \varepsilon_5^0 \\ \kappa_4^2 \\ \kappa_5^2 \end{Bmatrix} \end{aligned} \quad (6)$$

Where: $\begin{bmatrix} \varepsilon_1^0 & \varepsilon_2^0 & \varepsilon_6^0 & \kappa_1^0 & \kappa_2^0 & \kappa_6^0 & \kappa_1^2 & \kappa_2^2 & \kappa_6^2 \end{bmatrix}^T = [\varepsilon^0 \ \kappa^0 \ \kappa^2]^T$;

$$\begin{bmatrix} \varepsilon_4^0 & \varepsilon_5^0 & \kappa_4^2 & \kappa_5^2 \end{bmatrix}^T = [\gamma^s \ \kappa^1]^T$$

Where:

$$(A_{ij}, B_{ij}, D_{ij}, E_{ij}, F_{ij}, H_{ij}) = \sum_{k=1}^n \int_{h_{k-1}}^{h_k} \bar{C}_{ij}(1, z, z^2, z^3, z^4, z^6) dz, \quad (i, j = 1, 2, 6)$$

$$(A_{ij}, D_{ij}, F_{ij}) = \sum_{k=1}^n \int_{h_{k-1}}^{h_k} \bar{C}_{ij}(1, z^2, z^4) dz, \quad (i, j = 4, 5)$$

Substituting the resulting forces defined in equation (5), we obtain:

$$\begin{aligned} & \int_A (\delta \varepsilon^{0T} [A] \varepsilon^0 + \delta \varepsilon^{0T} [B] \kappa^0 + \delta \varepsilon^{0T} [E] \kappa^2 + \delta \kappa^{0T} [B] \varepsilon^0 + \delta \kappa^{0T} [D] \kappa^0 \\ & + \delta \kappa^{0T} [F] \kappa^2 + \delta \kappa^{2T} [E] \varepsilon^0 + \delta \kappa^{2T} [F] \kappa^0 + \delta \kappa^{2T} [H] \kappa^2 + \delta \gamma^{sT} [A^s] \gamma^s \\ & + \delta \gamma^{sT} [D^s] \kappa^s + \delta \kappa^{sT} [D^s] \gamma^s + \delta \kappa^{sT} [F^s] \kappa^s + \varepsilon^{sT} \{N\} + q \delta w) dA = 0 \end{aligned} \quad (7)$$

V. FINITE ELEMENT FORMULATION

The present finite element is a C_0 four nodes isoparametric having seven DOF for each node (Fig. 2). Three displacements u, v, w , two rotations ψ_x, ψ_y and two higher order rotations θ_x, θ_y where $\theta_x = (\psi_x + \partial w / \partial x)$, $\theta_y = (\psi_y + \partial w / \partial y)$. The analytical integration can be converted to Gauss's numerical integration [18]. For more model performance in terms of accuracy and stability and to avoid shear locking problem, the technical selective numerical integration is used from Gauss points (2x2) for membrane and flexional contribution and (1x1) point for the transverse shear contribution.

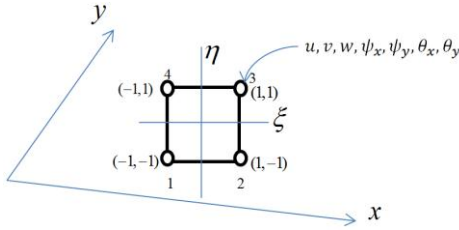


Fig. 2 Description of the normalized isoparametric element

A. Nodal approximation

The nodal approximation is expressed from the Lagrange interpolation concerning the considered degrees of freedom in each node and the element geometry through all coordinates (ζ, η) , the field variables may be expressed as follows:

$$\begin{aligned} u(\xi, \eta) &= \sum_{i=1}^4 \bar{N}_i(\xi, \eta) u_i; \quad v(\xi, \eta) = \sum_{i=1}^4 \bar{N}_i(\xi, \eta) v_i; \quad w(\xi, \eta) = \sum_{i=1}^4 \bar{N}_i(\xi, \eta) w_i; \\ \psi_x(\xi, \eta) &= \sum_{i=1}^4 \bar{N}_i(\xi, \eta) \psi_{xi}; \quad \psi_y(\xi, \eta) = \sum_{i=1}^4 \bar{N}_i(\xi, \eta) \psi_{yi}; \quad \theta_x(\xi, \eta) = \sum_{i=1}^4 \bar{N}_i(\xi, \eta) \theta_{xi}; \\ \theta_y(\xi, \eta) &= \sum_{i=1}^4 \bar{N}_i(\xi, \eta) \theta_{yi}; \quad x = \sum_{i=1}^4 \bar{N}_i(\xi, \eta) x_i; \quad y = \sum_{i=1}^4 \bar{N}_i(\xi, \eta) y_i, \end{aligned}$$

$$\text{Where: } \bar{N}_i(\xi, \eta) = \frac{1}{4} (1 + \xi \xi_i) (1 + \eta \eta_i)$$

$\bar{N}_i(\zeta, \eta)$ are the bi linear interpolation functions of Lagrange type corresponding to node $i=1, 2, 3, 4$ [19].

B. Deformation and nodal displacements relation

The deformation vectors and the nodal unknowns can be taken as the elementary nodal matrix forms as follows:

$$\varepsilon^0 = [B_\varepsilon^0]^T \{\delta\} = \begin{bmatrix} \frac{\partial \bar{N}_i}{\partial x} & 0 & 0 & 0 & 0 & 0 & 0 \\ 0 & \frac{\partial \bar{N}_i}{\partial y} & 0 & 0 & 0 & 0 & 0 \\ \frac{\partial \bar{N}_i}{\partial y} & \frac{\partial \bar{N}_i}{\partial x} & 0 & 0 & 0 & 0 & 0 \end{bmatrix} \begin{Bmatrix} u_i \\ v_i \\ w_i \\ \psi_{xi} \\ \psi_{yi} \\ \theta_{xi} \\ \theta_{yi} \end{Bmatrix}$$

$$\kappa^0 = [B_\kappa^0]^T \{\delta\} = \begin{bmatrix} 0 & 0 & 0 & \frac{\partial \bar{N}_i}{\partial x} & 0 & 0 & 0 \\ 0 & 0 & 0 & 0 & \frac{\partial \bar{N}_i}{\partial y} & 0 & 0 \\ 0 & 0 & 0 & \frac{\partial \bar{N}_i}{\partial y} & \frac{\partial \bar{N}_i}{\partial x} & 0 & 0 \end{bmatrix} \begin{Bmatrix} u_i \\ v_i \\ w_i \\ \psi_{xi} \\ \psi_{yi} \\ \theta_{xi} \\ \theta_{yi} \end{Bmatrix}$$

$$\kappa^2 = [B_\kappa^2]^T \{\delta\} = c_1 \begin{bmatrix} 0 & 0 & 0 & 0 & \frac{\partial \bar{N}_i}{\partial x} & 0 \\ 0 & 0 & 0 & 0 & 0 & \frac{\partial \bar{N}_i}{\partial y} \\ 0 & 0 & 0 & 0 & \frac{\partial \bar{N}_i}{\partial y} & \frac{\partial \bar{N}_i}{\partial x} \end{bmatrix} \begin{Bmatrix} u_i \\ v_i \\ w_i \\ \psi_{xi} \\ \psi_{yi} \\ \theta_{xi} \\ \theta_{yi} \end{Bmatrix}$$

$$\gamma^s = [B_\gamma^s]^T \{\delta\} = \begin{bmatrix} 0 & 0 & \frac{\partial \bar{N}_i}{\partial y} & 0 & \bar{N}_i & 0 & 0 \\ 0 & 0 & \frac{\partial \bar{N}_i}{\partial x} & \bar{N}_i & 0 & 0 & 0 \end{bmatrix} \begin{Bmatrix} u_i \\ v_i \\ w_i \\ \psi_{xi} \\ \psi_{yi} \\ \theta_{xi} \\ \theta_{yi} \end{Bmatrix}$$

$$\kappa^s = [B_\kappa^s]^T \{\delta\} = c_2 \begin{bmatrix} 0 & 0 & 0 & 0 & 0 & 0 & \bar{N}_i \\ 0 & 0 & 0 & 0 & 0 & 0 &; \bar{N}_i \end{bmatrix} \begin{Bmatrix} u_i \\ v_i \\ w_i \\ \psi_{xi} \\ \psi_{yi} \\ \theta_{xi} \\ \theta_{yi} \end{Bmatrix}$$

With: $c_1 = -4/3h^2$, $c_2 = -4/h^2$

According to the substitution of deformation and nodal displacements relations in the equilibrium equation (7) and from the static system $[K]_e \{\delta\} = \{F\}$ we can conclude the elementary stiffness matrix $[K]_e$ as follow:

$$\begin{aligned} [K]_e &= \int_{-1}^1 \int_{-1}^1 ([B_\varepsilon^0]^T [A] [B_\varepsilon^0] + [B_\varepsilon^0]^T [B] [B_\varepsilon^0] + [B_\varepsilon^0]^T [E] [B_\varepsilon^0] + [B_\varepsilon^0]^T [B] [B_\varepsilon^0] + \\ & [B_\varepsilon^0]^T [D] [B_\varepsilon^0] + [B_\varepsilon^0]^T [F] [B_\varepsilon^0] + [B_\varepsilon^0]^T [E] [B_\varepsilon^0] + [B_\varepsilon^0]^T [F] [B_\varepsilon^0] + [B_\varepsilon^0]^T [H] [B_\varepsilon^0] + \\ & [B_\varepsilon^0]^T [A^s] [B_\varepsilon^0] + [B_\varepsilon^0]^T [D^s] [B_\varepsilon^0] + [B_\varepsilon^0]^T [D^s] [B_\varepsilon^0] + [B_\varepsilon^0]^T [F^s] [B_\varepsilon^0]) \det[J] d\xi d\eta \quad (8) \end{aligned}$$

Where $\{F\}, \{\delta\}$ are the elementary nodal vectors of forces and unknowns displacement, respectively.

VI. RESULTS AND DISCUSSION

A. Convergence study

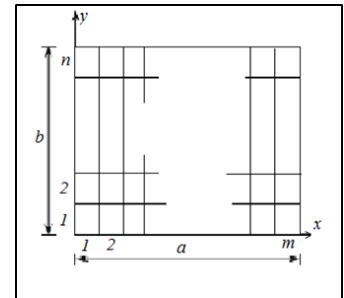


Fig. 3. Regular mesh of rectangular plate $m \times n$

1) *Exemple 1*

In the first example, the convergence of the developed quadrilateral element is studied for a simply supported isotropic square plate subjected to uniformly distributed load. Two thickness ratios ($a/h=10, 100$) are considered for the analysis. The non-dimensional results of transverse displacement, for different mesh sizes are displayed on Table 1.

The non-dimensional transverse displacement value is described from: $\bar{w}=100wD/qa^4$ where: $D=Eh^2/12(1-\nu^2)$ with $\nu=0.3$.

The comparison was made with the analytical solutions given by Reddy [14]. The results of the comparison show the performances and convergence of the present formulation. It can be noticed that the present model is applicable in both thick and thin isotropic plates.

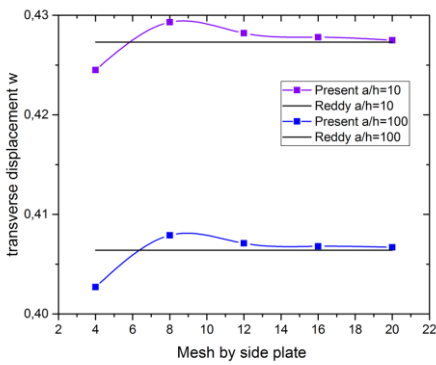


Fig. 4. Convergence test of transverse displacement of an isotropic square plate simply supported under uniform loading.

2) *Exemple 2*

In this example, we consider a simply supported square three-layer (0/90/0) symmetrical cross-ply laminated plate subjected to a sinusoidal load L_1 , and properties material $E_1/E_2=25, G_{12}=G_{13}=0.5E_2, G_{23}=0.2E_2, \nu=0.25$. The nondimensional central deflexion and maximum stresses of the plate have been determined for different thickness ratio a/h . Very satisfactory results have been obtained in Table. 2 for a mesh size of 16×16 comparing to those obtained analytically by the Pagano's 3D Elasticity solution [7, 24], Reddy [12] and Wang and Shi [25] and those obtained by other finite elements models based on different theories as HSDT and the first order FSDT by Sheikh [14] and TSDT layer-wise by Ramesh et al.[26].

TABLE I. NONDIMENSIONAL DEFLEXION AND STRESSES OF A SQUARE LAMINATED PLATE (0/90/0) UNDER A SINUSOIDAL LOAD

| Reference | Theory | $\frac{a}{h}$ | \bar{w} | $\bar{\sigma}_{xx}$ | $\bar{\sigma}_{yy}$ | $-\bar{\sigma}_{xy}$ | $\bar{\sigma}_{xz}$ | $\bar{\sigma}_{yz}$ |
|-------------------|------------|---------------|-----------|---------------------|---------------------|----------------------|---------------------|---------------------|
| Present | TSQ28 | 4 | 1.936 | 0.7657 | 0.5073 | 0.0495 | 0.2061 | 0.1797 |
| Pagano [7, 24] | Elasticity | | 2.0042 | 0.8010 | 0.534 | 0.0505 | 0.256 | 0.2172 |
| Wang and Shi [25] | HSDT | | 1.9734 | 0.8439 | 0.5972 | 0.0508 | 0.2409 | 0.2297 |
| Reddy[12] | TSDT | | 1.9218 | 0.7345 | - | - | - | 0.1832 |

| | | | | | | | | |
|--------------------|---------------------|--------|--------|--------|--------|--------|--------|--------|
| Sheikh [14] | HSDT(FE) | 10 | 1.923 | 0.7500 | 0.5080 | 0.0499 | 0.2023 | 0.1831 |
| Sheikh [14] | FSDT(FE) | | 1.777 | 0.4430 | 0.4843 | 0.0371 | 0.1440 | 0.1569 |
| Ramesh et al. [26] | TSDT layer-wise(FE) | | 1.9136 | 0.7672 | 0.5081 | 0.0500 | 0.2809 | 0.2103 |
| Present | TSQ28 | | 0.7198 | 0.5833 | 0.2709 | 0.0278 | 0.2610 | 0.1017 |
| Pagano [7, 24] | Elasticity | | 0.7405 | 0.5900 | 0.285 | 0.0289 | 0.3570 | 0.1228 |
| Wang and Shi [25] | HSDT | | 0.7549 | 0.5946 | 0.2919 | 0.029 | 0.3566 | 0.1239 |
| Reddy[12] | TSDT | | 0.7125 | 0.5684 | - | - | - | 0.1033 |
| Sheikh [14] | HSDT(FE) | | 0.7140 | 0.5806 | 0.2722 | 0.0279 | 0.2437 | 0.1015 |
| Sheikh [14] | FSDT(FE) | | 0.6700 | 0.5219 | 0.2582 | 0.025 | 0.1623 | 0.0918 |
| Ramesh et al. [26] | TSDT layer-wise(FE) | | 0.7178 | 0.5850 | 0.2713 | 0.0281 | 0.3671 | 0.1178 |
| Present | TSQ28 | | 0.5065 | 0.5492 | 0.2046 | 0.0229 | 0.2745 | 0.0808 |
| Pagano [7, 24] | Elasticity | | 0.5142 | 0.552 | 0.210 | 0.0234 | 0.3850 | 0.0938 |
| Wang and Shi [25] | HSDT | 0.5176 | 0.553 | 0.2106 | 0.0234 | 0.3845 | 0.094 | |
| Ramesh et al. [26] | TSDT layer-wise(FE) | 0.5060 | 0.5509 | 0.2050 | 0.0231 | 0.3871 | 0.0917 | |
| Present | TSQ28 | 0.4344 | 0.5376 | 0.1801 | 0.0211 | 0.2794 | 0.0731 | |
| Pagano [7, 24] | Elasticity | 0.4368 | 0.5390 | 0.1810 | 0.0213 | 0.3950 | 0.0828 | |
| Wang and Shi [25] | HSDT | 0.4356 | 0.5392 | 0.1808 | 0.0214 | 0.3946 | 0.0829 | |
| Reddy[12] | TSDT | 0.4342 | 0.5390 | - | - | - | 0.0750 | |
| Sheikh [14] | HSDT(FE) | 0.4350 | 0.5496 | 0.1828 | 0.0215 | 0.2401 | 0.0749 | |
| Sheikh [14] | FSDT(FE) | 0.4350 | 0.5490 | 0.1825 | 0.0202 | 0.1568 | 0.0709 | |
| Ramesh et al. [26] | TSDT layer-wise(FE) | 0.4345 | 0.5394 | 0.1806 | 0.0214 | 0.3952 | 0.0835 | |


The nondimensional values are described in Table. 4 as given by:

$$\bar{w} = w \left(\frac{a}{2}, \frac{b}{2}, 0 \right) (h^3 E_2 / q_0 a^4) 10^2, \bar{\sigma}_{xx} = \sigma_{xx} \left(\frac{a}{2}, \frac{b}{2}, \frac{h}{2} \right) (h^2 / q_0 a^2), \bar{\sigma}_{yy} = \sigma_{yy} \left(\frac{a}{2}, \frac{b}{2}, \frac{h}{6} \right) (h^2 / q_0 a^2),$$

$$\bar{\sigma}_{xy} = \sigma_{xy} \left(0, 0, \frac{h}{2} \right) (h^2 / q_0 a^2), \bar{\sigma}_{xz} = \sigma_{xz} \left(0, \frac{b}{2}, 0 \right) (h / q_0 a), \bar{\sigma}_{yz} = \sigma_{yz} \left(\frac{a}{2}, 0, 0 \right) (h / q_0 a)$$

a) *Distribution of stress through the sandwich plate thickness*

In Figs (5 (a,b), 6(a,b,c)), the curves show good distributions obtained of normal stresses σ_{xx}, σ_{yy} through the thickness of the sandwich plate with ratio $a/b=4, 10$ by comparing to those obtained analytically by Pagano's Elasticity [27].

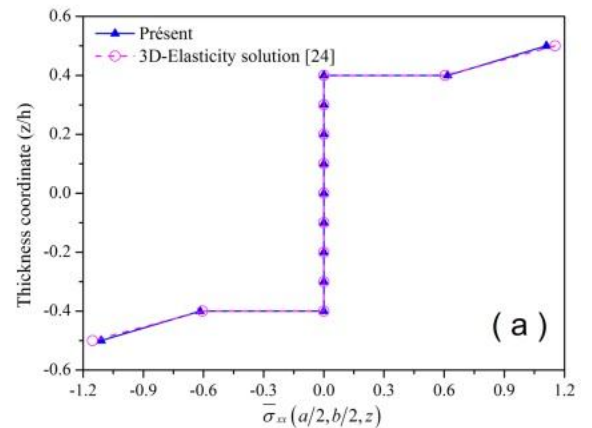

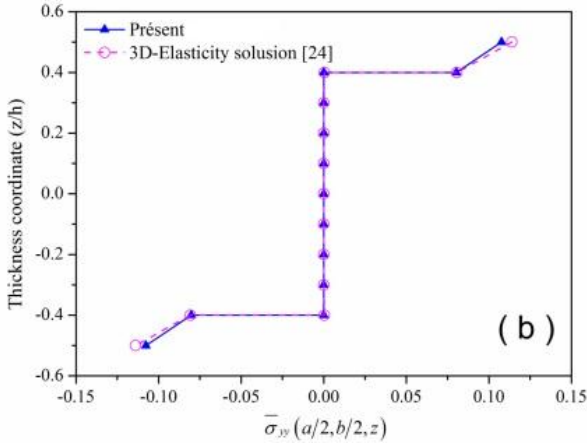


Fig 5. Distribution of the normal stress σ_{xx} , σ_{yy} through the thickness of a simply supported sandwich plate subjected to a sinusoidal load ratio of $a/h = 10$

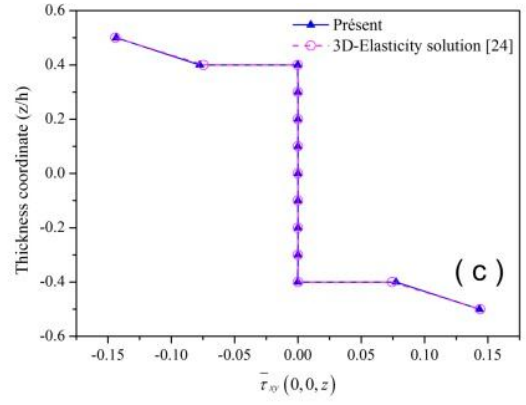
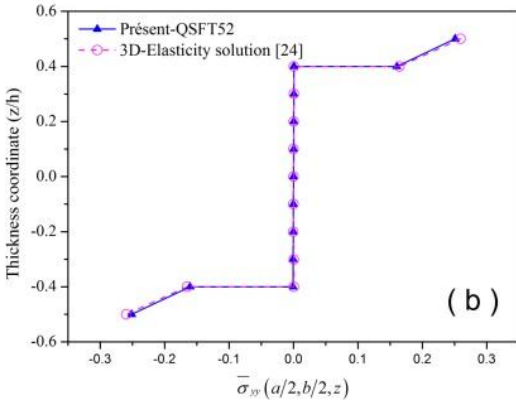
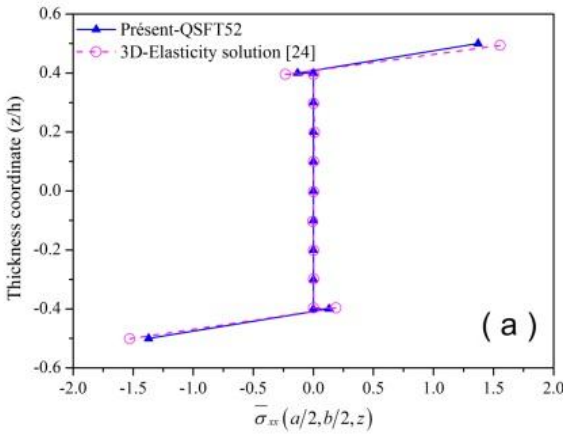


Fig 6. Distribution of the normal stress σ_{xx} , σ_{yy} , σ_{xy} through the thickness of a simply supported sandwich plate subjected to a sinusoidal load ratio of $a/h = 4$

VII. CONCLUSION

In this paper, a developed four nodes isoparametric finite element is proposed on the basis on Reddy's third order shear deformation theory by adopting the equivalent single-layer approach. The present element has seven degrees of freedom for each node, three displacements, two rotations and two higher order rotations. The formulation is able to take into account the transverse shear effect in order to analyze the bending behavior of isotropic, sandwich and laminated composite thin and thick plates without to need correction factors. Furthermore, the selective numerical integration technique is conducted in order to get accurate results without including numerical locking problem.

References

- [1] Mouritz, A., et al., *Review of advanced composite structures for naval ships and submarines*. Composite Structures, 2001. **53**(1): p. 21-42.
- [2] Reddy, J., *An evaluation of equivalent-single-layer and layerwise theories of composite laminates*. Composite Structures, 1993. **25**(1): p. 21-35.
- [3] Kirchhoff, G., *Über die Schwingungen einer kreisförmigen elastischen Scheibe*. Annalen der Physik, 1850. **157**(10): p. 258-264.
- [4] Love, A.E.H., *A treatise on the mathematical theory of elasticity* 2013: Cambridge University Press.
- [5] Reissner, E., *The effect of transverse shear deformations on the bending of elastic plates*. Journal of Applied Mechanics, 1945. **12**: p. A69-A77.
- [6] Whitney, J.M., *The Effect of Transverse Shear Deformation on the Bending of Laminated Plates*. Journal of Composite Materials, 1969. **3**(3): p. 534-547.
- [7] Pagano, N., *Exact solutions for composite laminates in cylindrical bending*. Journal of Composite Materials, 1969. **3**(3): p. 398-411.
- [8] Whitney, J., *Shear correction factors for orthotropic laminates under static load*. Journal of Applied Mechanics, 1973. **40**(1): p. 302-304.
- [9] Stavsky, Y. and R. Loewy, *On vibrations of heterogeneous orthotropic cylindrical shells*. Journal of Sound and Vibration, 1971. **15**(2): p. 235-256.
- [10] Reddy, J. and D. Robbins, *Theories and computational models for composite laminates*. Applied Mechanics Reviews, 1994. **47**(6): p. 147-169.

- [11] Ghugal, Y. and R. Shimpi, *A review of refined shear deformation theories of isotropic and anisotropic laminated plates*. Journal of Reinforced Plastics and Composites, 2002. **21**(9): p. 775-813.
- [12] Reddy, J.N., *A simple higher-order theory for laminated composite plates*. Journal of Applied Mechanics, 1984(a). **51**(4): p. 745-752.
- [13] Reddy, J.N., *A refined nonlinear theory of plates with transverse shear deformation*. International Journal of Solids and Structures, 1984(c). **20**(9): p. 881-896.
- [14] Sheikh, A.H. and A. Chakrabarti, *A new plate bending element based on higher-order shear deformation theory for the analysis of composite plates*. Finite Elements in Analysis and Design, 2003. **39**(9): p. 883-903.
- [15] Batoz, J.L. and M.B. Tahar, *Evaluation of a new quadrilateral thin plate bending element*. International Journal for Numerical Methods in Engineering, 1982. **18**(11): p. 1655-1677.
- [16] Zhang, Y. and C. Yang, *Recent developments in finite element analysis for laminated composite plates*. Composite Structures, 2009. **88**(1): p. 147-157.
- [17] Reddy, J.N., *Mechanics of laminated composite plates and shells: Theory and analysis*. Second Edition ed2004, Boca Raton, FL: CRC Press.
- [18] Hughes, T.J., M. Cohen, and M. Haroun, *Reduced and selective integration techniques in the finite element analysis of plates*. Nuclear Engineering and Design, 1978. **46**(1): p. 203-222.
- [19] Zienkiewicz, O.C. and Y.K. Cheung, *The finite element method for analysis of elastic isotropic and orthotropic slabs*. in *ICE Proceedings*. 1964. Thomas Telford.
- [20] Kant, T., *Numerical analysis of thick plates*. Computer methods in applied mechanics and engineering, 1982. **31**(1): p. 1-18.
- [21] Dobyns, A., *Analysis of simply-supported orthotropic plates subject to static and dynamic loads*. AIAA Journal, 1981. **19**(5): p. 642-650.
- [22] Kant, T., D. Owen, and O. Zienkiewicz, *A refined higher-order C^0 plate bending element*. Computers & structures, 1982. **15**(2): p. 177-183.
- [23] Goswami, S. and W. Becker, *A New Rectangular Finite Element Formulation Based on Higher Order Displacement Theory for Thick and Thin Composite and Sandwich Plates*. World Journal of Mechanics, 2013. **3**(03): p. 194.
- [24] Pagano, N., *Exact solutions for rectangular bidirectional composites and sandwich plates*. Journal of Composite Materials, 1970. **4**(1): p. 20-34.
- [25] Wang, X. and G. Shi, *A refined laminated plate theory accounting for the third-order shear deformation and interlaminar transverse stress continuity*. Applied Mathematical Modelling, 2015. **39**(18): p. 5659-5680.
- [26] Ramesh, S.S., et al., *A higher-order plate element for accurate prediction of interlaminar stresses in laminated composite plates*. Composite Structures, 2009. **91**(3): p. 337-357.
- [27] Soldatos, K., *A transverse shear deformation theory for homogeneous monoclinic plates*. Acta Mechanica, 1992. **94**(3-4): p. 195-220.